arXiv:cond-mat/9912221v1 [cond-mat.str-el] 13 Dec 1999

Reply to "Comment on 'Inverse exciton series in the optical decay of an excitonic molecule' "

Eiji Tokunaga,[1] A.L. Ivanov,[2] Selvakumar V. Nair,[1] and Yasuaki Masumoto[1,3]
[1]*ERATO Single Quantum Dot Project, Japan Science and Technology Corporation, 5-9-9 Tokodai, Tsukuba 300-2635, Japan*
[2] *TCM, Cavendish Laboratory, University of Cambridge, UK*
[3]*Institute of Physics, University of Tsukuba, Tsukuba 305-8571, Japan*
(February 1, 2008)

As a reply to the Comment by I.S. Gorban *et al.* (Phys. Rev. B, preceding paper) we summarize our criticism on their claim of the first observation of the M series in β-ZnP_2. We support our analysis by reporting the first observation of inverse *polariton* series from the excitonic molecules selectively generated at $\mathbf{K}_m \simeq \mathbf{0}$ in a CuCl single crystal. This observation and its explanation within the bipolariton model complete our proof of the biexcitonic origin of the inverse series.

71.35.-y; 71.36.+c; 78.55.-m; 33.80.-b

A monocrystal CuCl is a prototype material in the physics of excitonic molecules, due to the polarization isotropy of the optical transitions to the excitonic states and due to the large binding energy of the molecules $\epsilon^m \simeq$ 32 meV [1]. In a recent paper [2] we reported the observation of the M series, which originates from the optical decay of the molecules into the excitonic states $1s$, $2s$, $3s$, $4s$, and ∞s. The lines $M_{n\geq 2s}$ are extremely weak and their detection requires a very modern spectroscopic technique and a high-quality CuCl single crystal. In our paper we explained briefly why the claim by Gorban *et al.* [3–5] to the observation of the M series in β-ZnP_2 is not justified (see reference [17] of Ref. [2]). By their Comment [6] the authors force us to present a more detailed criticism of their experiments.

Monoclinic zinc diphosphide (β-ZnP_2) is an optically highly-anisotropic semiconductor with eight molecules per unit cell, which give rise to 72 phonon modes. As a result, the excitonic spectra are very complicated and strongly depend on the excitation and polarization geometry. Thus the correct interpretation of the optical spectra of β-ZnP_2 requires a very accurate experiment, a high-quality sample, and a critical analysis of the experimental data. The first reports [7] on the observation of the inverse hydrogen-like series in β-ZnP_2 attribute the series to a bielectron-impurity complex. To the best of our knowledge, these results have never been confirmed. The next reports [3,4] on the inverse series ascribe the photoluminescence (PL) spectra of highly-excited β-ZnP_2 to the M series. Even without commenting on Gorban *et al.*'s experiments, we will show below that their interpretation of the PL spectra in terms of the M series is self-contradictory and incorrect.

Firstly, from their experimental data Gorban *et al.* conclude that the biexciton binding energy ϵ^m in β-ZnP_2 is unusually high, i.e., $\epsilon^m = 14.9$ meV (0.32 of the excitonic Rydberg ϵ^x). In order to explain this result the authors claim without any justifications that the relevant electron and hole effective masses in β-ZnP_2 are given by $m_e = 1.7m_0$ and $m_h = 21.3m_0$ ($\sigma = m_e/m_h = 0.08$) [4]. This strongly contradicts the Kane model, which basically requires $m_h \sim m_0$, and the first experiments [8] on excitonic polaritons in β-ZnP_2 which yield the effective excitonic mass $M_x = m_e + m_h \leq 3m_0$. The latest high-precision experiments by two-photon and magneto-optical spectroscopies [9] indicate the high anisotropy of β-ZnP_2 single crystals with $m_e = 0.7m_0$, $m_h = 1.1m_0$ along the a-axis, $m_e = 1.1m_0$, $m_h = 1.4m_0$ along the b-axis, and $m_e = 0.18m_0$, $m_h = 0.20m_0$ along the c-axis, respectively. These values clearly demonstrate that the effective masses chosen by Gorban *et al.* are irrelevant. Furthermore, with reference to $\sigma = 0.08$ the authors claim that their $\epsilon^m = 0.32\epsilon^x$ "corresponds to the variational calculations of Refs. [10,11]" (see p. 339 of Ref. [4]). This is a misinterpretation of the theoretical results of Refs. [10,11]. An inspection of Fig. 1 of Ref. [10] and Fig. 3 of Ref. [11] shows that the mass ratio $\sigma = 0.08$ yields $\epsilon^m \simeq 0.12\epsilon^x$. As a result, even for the above incorrect value of the ratio m_e/m_h the molecule binding energy should be only $\epsilon^m = 5.64$ meV rather than 14.9 meV.

Secondly, the intensity ratio between two main replicas of the series reported by Gorban *et al.* is too high to be ascribed to the M series. The intensity ratio of two lines marked by M_1 and M_2 in Fig. 1 of Ref. [4] is given by $I_{M_2}/I_{M_1} \simeq 1/3$ ($I_{M_1} = I_{M_{1T}} + I_{M_{1L}}$). In Ref. [5] the authors explain that the above ratio should be corrected due to the saturation of the M_{1T} line and that the true value is $I_{M_2}/I_{M_1} \simeq 1/9.08$ as shown in the intensity dependence in Fig. 2 of Ref. [4]. The bipolariton model [12] with the Akimoto-Hanamura trial wave function [10] yields $I_{M_2}/I_{M_1} \simeq 1/5000$ for excitonic molecules in CuCl (the electron-hole mass ratio $\sigma = 0.28$). This value is in agreement with our experiments, which indicate $I_{M_2}/I_{M_1} \simeq 1/7000$. Using a precise wave function of the hydrogen molecule [13], we find $I_{M_2}/I_{M_1} \simeq 1/800$ in the limit $\sigma = 0$. Thus, within the uncertainty in the value of σ in β-ZnP_2, we estimate, for excitonic molecules in this semiconductor, $I_{M_2}/I_{M_1} \leq 1/1000$. The latter value is at least two orders of magnitude smaller than that reported by Gorban *et al.* [3,4]. Note that in the Comment [6] the authors have corrected their intensity ratio as $I_{M_2}/I_{M_1} \simeq 1/230$ referring to the *new* intensity dependence in Fig. 2 of the Comment, but this intensity dependence contradicts that reported in Fig. 2 of Ref. [4].

The low-temperature PL spectra of β-ZnP_2 single crystals at moderate optical excitations have been studied in Ref. [14]. According to Ref. [14], the M_1 emission band indeed develops at an optical excitation power of about 10 kW/cm^2, however, without any indications of the M series. Instead, below the M_1 band another PL line arises (at 1.523 eV), which grows quadratically with the excitation intensity and has a comparable intensity with the M_1 band. This M-like emission line is attributed to excitonic molecules trapped by surface defects, because a similar spectral line is presented in the reflection spectra but is absent in the absorption spectra. Furthermore, the line is not reproducible from sample to sample but found only for a few samples. Note that the above described M-like emission at 1.523 eV exactly coincides with the PL line labeled by M_2 in Fig. 1 of the Comment (see also Fig. 1 of Ref. [4]). According to Ref. [15], the molecule energy is 3.1102 ± 0.0002 eV. Therefore the inverse M_2 emission should arise at 1.519 eV, rather than at 1.523 eV in the Gorban *et al.*'s data.

Because of its extremely weak intensity, the confirmation of the inverse series requires many severe experimental checks. The two-photon resonant generation of excitonic molecules with translational momentum $\hbar\mathbf{K}_m$ is crucial for unambiguous discrimination of the M series in our experiments. In Fig. 1 we compare the PL spectra of a high-quality CuCl single crystal (sample *No.* 1)

recorded under the selective excitation of the molecules at $\mathbf{K}_m = 2\mathbf{k}_0$ (solid curve) and under the interband excitation (dashed curve). Here $\mathbf{k}_0$ is the wave vector of the pump polaritons. In the latter case the M_T and M_L emission lines are absent because of weak cw-laser excitation, but only $1s$ exciton emissions and the relavant bound exciton lines are present. As shown by the solid curve, even under the two-photon excitation of the molecules, bound exciton structures similar to those in the dashed curve grow quadratically with the excitation intensity together with the M series. They originate from the secondary excitons generated by the molecule decay. As shown by the dashed curve, an emission from impurity-bound excitons occurs at 3.082 eV. Therefore, the line marked by $M_{Z_{1,2}}$ cannot be attributed to the inverse series, although its energy coincides with the molecule emission leaving the longitudinal $Z_{1,2}$ exciton behind [16]. On the other hand, our samples are free from any impurity emissions at the spectral position of the $M_{2s} - M_{\infty s}$ lines. Thus we assign these lines to the inverse M series. Furthermore, we checked the reproducibility of the $M_{2s,3s,4s}$ series for several high-quality samples of a CuCl single crystal. Figure 2 shows the PL spectrum of sample $No.$ 2 under resonant generation of excitonic molecules at $\mathbf{K}_m = 2\mathbf{k}_0$. The period of interference pattern of sample $No.$ 2 is different from that of sample $No.$ 1. However, the characteristics of the M series are identical for both samples.

At the present time we have improved the experimental setup and can observe the optical decay of excitonic molecules selectively excited at various $\mathbf{K}_m$ ($0 \leq K_m \leq 2k_0$). Figure 3 shows the inverse emission series from excitonic molecules with $\mathbf{K}_m \simeq \mathbf{0}$. Now the molecule cannot decay into the pure excitonic states $1s$, $2s$, ..., but resonantly dissociates into two outgoing polaritons associated with the corresponding optical transitions. Thus the M series of Fig. 3 is described as an inverse *polariton* series. Because the main contribution to the series is due to the resonant dissociation of the molecule into the lower dispersion branch polaritons, we designate the series by LP_{ns}. Note that the intensity ratio $I_{LP_{2s}}/I_{LP_{1s}}$ is about 1/100, i.e., by two orders of magnitude larger than $I_{M_{2s}}/I_{M_{1s}}$ corresponding to the molecules initially photogenerated at $\mathbf{K}_m = 2\mathbf{k}_0$ [2]. With the bipolariton model of an excitonic molecule [12], both of the inverse series, M_{ns} of Fig. 1 and LP_{ns} of Fig. 3, are explained self-consistently using the same trial molecule wave function [17]. This completes our proof of the biexcitonic origin of the inverse series observed in CuCl single crystals. The use of a weak selective resonant excitation of the molecules allows us to avoid the nonlinear reabsorption processes and a thermal distribution of the molecules which considerably changes the intensity ratios of the inverse series.

In their experiments [3,4,6], Gorban *et al.* have used only the interband excitation of β-ZnP_2. Such an excitation is not suitable for the discrimination of the M series as we have shown above. Furthermore, while the authors do not observe their M series at moderate interband excitations of β-ZnP_2 (Ar-laser of a few kW/cm^2 intensity), they describe a corresponding rich PL spectrum mainly in terms of the optical decay of nonlocalized excitonic molecules (see the lines marked by M_1, C, and G in Fig. 3 of Ref. [4]). According to Gorban *et al.*, the G-band is due to the degenerate two-photon radiative annihilation of biexcitons with $\mathbf{K}_m \simeq \mathbf{0}$ and the C-line is due to a "dielectric liquid" of excitonic molecules. We consider this interpretation as absolutely speculative and unjustified. In particular, the M_{1s} band of thermally distributed excitonic molecules is not expected to show any fine structure due to the degenerate two-photon annihilation of the molecules [1,18]. Finally, if the nonlocalized biexcitons are mainly responsible for the complicated PL spectrum plotted in Fig. 3 of Ref. [4], as the authors incorrectly interpret, it is not understandable why in this case they do not observe their M series.

Once the inverse M-series is observed [2], the question on the reconstruction of the internal molecule wave function naturally arises. Here, the relevant theoretical questions are how the molecule decays radiatively to the ns exciton states and how the relative intensities of the M_{ns} replicas relate to the molecule wave function. The theory of the optical decay of an excitonic molecule presented by Gorban *et al.* [5] is incorrect.

Firstly, the use of Wang's trial wave function, Eq. (1) of Ref. [5], means that the biexciton is identified with the hydrogen molecule. The Wang wave function is suitable for H_2 due to the adiabatic approximation, which requires $(m_e/m_h)^{1/4} \ll 1$. The latter inequality definitely does not hold even for the incorrect ratio $m_e/m_h = 0.08$ used by the authors for biexcitons in β-ZnP_2. In other words, an envelope wave function for the relative motion of two constituent excitons is absent in Eq. (1) of Ref. [5]. However, the authors ignore the above standard arguments and take the results of the well-known calculations [19] on the hydrogen molecule with the same values of the fitting parameter ($Z = 1.166$) and binding energy (0.31 Rydberg). The Wang wave function is irrelevant for excitonic molecules. The corresponding evaluation of the molecule binding energy within the four-particle Schrödinger equation, claimed by the authors, cannot be reproduced.

Secondly, Eq. (2) of Ref. [5] proposed for the intensities of the M_{ns} replicas is incorrect, because (i) two of the arguments of the molecule wave function are fixed by $r_{a1} = 0$ and $r_{b1} = a_{biex}$, (ii) one additional integral convolution with the ground-state excitonic envelope wave function is absent (the integration over $d\mathbf{r}_{a1}$). As a result, the authors end up with an incorrect conclusion, that "the probability of the two-photon radiative transition is $\propto (a_{biex}/a_{ex})^6$, in contrast to the probability of the two-photon absorptive one which is $\propto (a_{biex}/a_{ex})^3$". Furthermore, Eq. (2) of Ref. [5] does not include the po-

lariton effects, i.e., the both crucial factors, the density of states and Hopfield's coefficients, are omitted.

Thirdly, the expansion of the molecule wave function given by Eq. (3) of Ref. [5] makes little sense, because (i) the biexciton wave function is assumed to be dependent only on two coordinates $\mathbf{r}_{a1}$ and $\mathbf{r}_{b2}$, while the correct wave function should be specified by *three* independent vector coordinates, (ii) the r.h.s. of Eq. (3) is not symmetric with respect to the permutation of two electrons or holes. The correct expansion of the molecule wave function is given by Eq. (5) of Ref. [2].

In order to assign the M-like emissions to the inverse exciton series one needs a severe critical analysis of the experimental data. While the observation of the M series in CuCl requires a highly sensitive detection technique and a high-quality sample free from impurity emissions, our results are very stable and reproducible. Furthermore, **k**-selective excitation of excitonic molecules is crucial both for the final evidence of the observation of the M series and for the reconstruction of the molecule wave function. The bipolariton model allows us to describe self-consistently a continuous, smooth change of the intensities and spectral positions of the M_{ns} replicas with the total molecular wavevector $\mathbf{K}_m$ decreasing from $2\mathbf{k}_0$ towards $\mathbf{K}_m = \mathbf{0}$ (compare Fig. 1 and Fig. 3). From the criteria discussed above we conclude that Gorban *et al.* have not yet presented a convincing set of the experimental data on the M series in β-ZnP_2.

[1] M. Ueta, H. Kanzaki, K. Kobayashi, Y. Toyozawa, and E. Hanamura, *Excitonic Processes in Solids*, Springer Series in Solid-State Sciences, Vol. 60 (Springer, Berlin, 1986), Chap. 2 and 3.

[2] E. Tokunaga, A.L. Ivanov, S.V. Nair, and Y. Masumoto, Phys. Rev. B **59**, R7837 (1999).

[3] M.M. Bilyi, I.S. Gorban, V.A. Gubanov, and I.M. Dmitruk, Pis'ma Zh. Eksp. Teor. Fiz. **50**, 75 (1989) [JETP Lett. **50**, 85 (1989)].

[4] I.S. Gorban, M.M. Bilyi, I.M. Dmitruk, and O.A. Yeshchenko, Phys. Status Solidi B **191**, 337 (1995).

[5] I.S. Gorban, I.M. Dmitruk, and O.A. Yeshchenko, Sold State Commun. **98**, 941 (1996).

[6] I.S. Gorban, M.M. Bilyi, I.M. Dmitruk, and O.A. Yeshchenko, Phys. Rev. B, preceding paper, (1999).

[7] A.V. Sel'kin, I.G. Stamov, N.N. Syrbu, and A.G. Umanets, Pis'ma Zh. Eksp. Teor. Fiz. **35**, 51 (1982) [JETP Lett. **35**, 57 (1982)]; N.N. Surbu, I.G. Stamov, and S.I. Radautsan, Dokl. Akad. Nauk SSSR **262**, 1138 (1982) [Sov. Phys. Dokl. **27**, 144 (1982)].

[8] A.B. Pevtsov, S.A. Permogorov, A.V. Sel'kin, N.N. Syrbu, and A.G. Umanets, Fiz. Tekh. Poluprovodn. **16**, 1399 (1982) [Sov. Phys. Semicond. **16**, 897 (1982)]; R.S. Berg, P.Y. Yu, and T. Mowles, Solid State Commun. **46**, 101 (1983).

[9] S. Taguchi, T. Goto, M. Takeda, and G. Kido, J. Phys. Soc. Jpn. **57**, 3256 (1988); D. Fröhlich, M. Schlierkamp, J. Schubert, S. Spitzer, O. Arimoto, and K. Nakamura, Phys. Rev. B **49**, 10337 (1994); S. Spitzer, PhD thesis, p. 76, Dortmund University (1996).

[10] O. Akimoto and E. Hanamura, J. Phys. Soc. Jpn. **33**, 1537 (1972).

[11] W.F. Brinkman, T.M. Rice, and B. Bell, Phys. Rev. B **8**, 1570 (1973).

[12] A.L. Ivanov, H. Haug, and L.V. Keldysh, Phys. Rep. **296**, 237 (1998); A.L. Ivanov, in *Microscopic Theory of Semiconductors: Quantum Kinetics, Confinement and Lasers*, ed. S.W. Koch (World Scientific, Singapore, 1996) pp. 359-399.

[13] W. Kolos and C.C.J. Roothaan, Rev. Mod. Phys. **32**, 219 (1960).

[14] K. Kondo, MSc thesis, Okayama University, (1998).

[15] T. Goto and Y. Goto, J. Phys. Soc. Jpn. **60**, 1763 (1991).

[16] M. Hasuo and N. Nagasawa, J. Lumin. **66 & 67**, 410 (1996).

[17] E. Tokunaga, A.L. Ivanov, S.V. Nair, and Y. Masumoto, unpublished.

[18] T. Anzai, T. Goto, and M. Ueta, J. Phys. Soc. Jpn. **38**, 774 (1975).

[19] S.C. Wang, Phys. Rev. **31**, 579 (1928).

FIG. 1. The photoluminescence spectra of a CuCl single crystal (sample *No.* 1) under the two-photon resonant generation of excitonic molecules $\mathbf{K}_m = 2\mathbf{k}_0$ by the ps laser pump at 3.186 eV (solid curves) and under the interband excitation at 3.814 eV (dashed curves) with a cw HeCd Laser.

FIG. 2. The inverse exciton series in the PL spectrum of a CuCl single crystal (sample *No.* 2) under the two-photon resonant excitation of molecules at $\mathbf{K}_m = 2\mathbf{k}_0$.

FIG. 3. The inverse polariton series (M series) from excitonic molecules resonantly created at $\mathbf{K}_m = \mathbf{0}$.

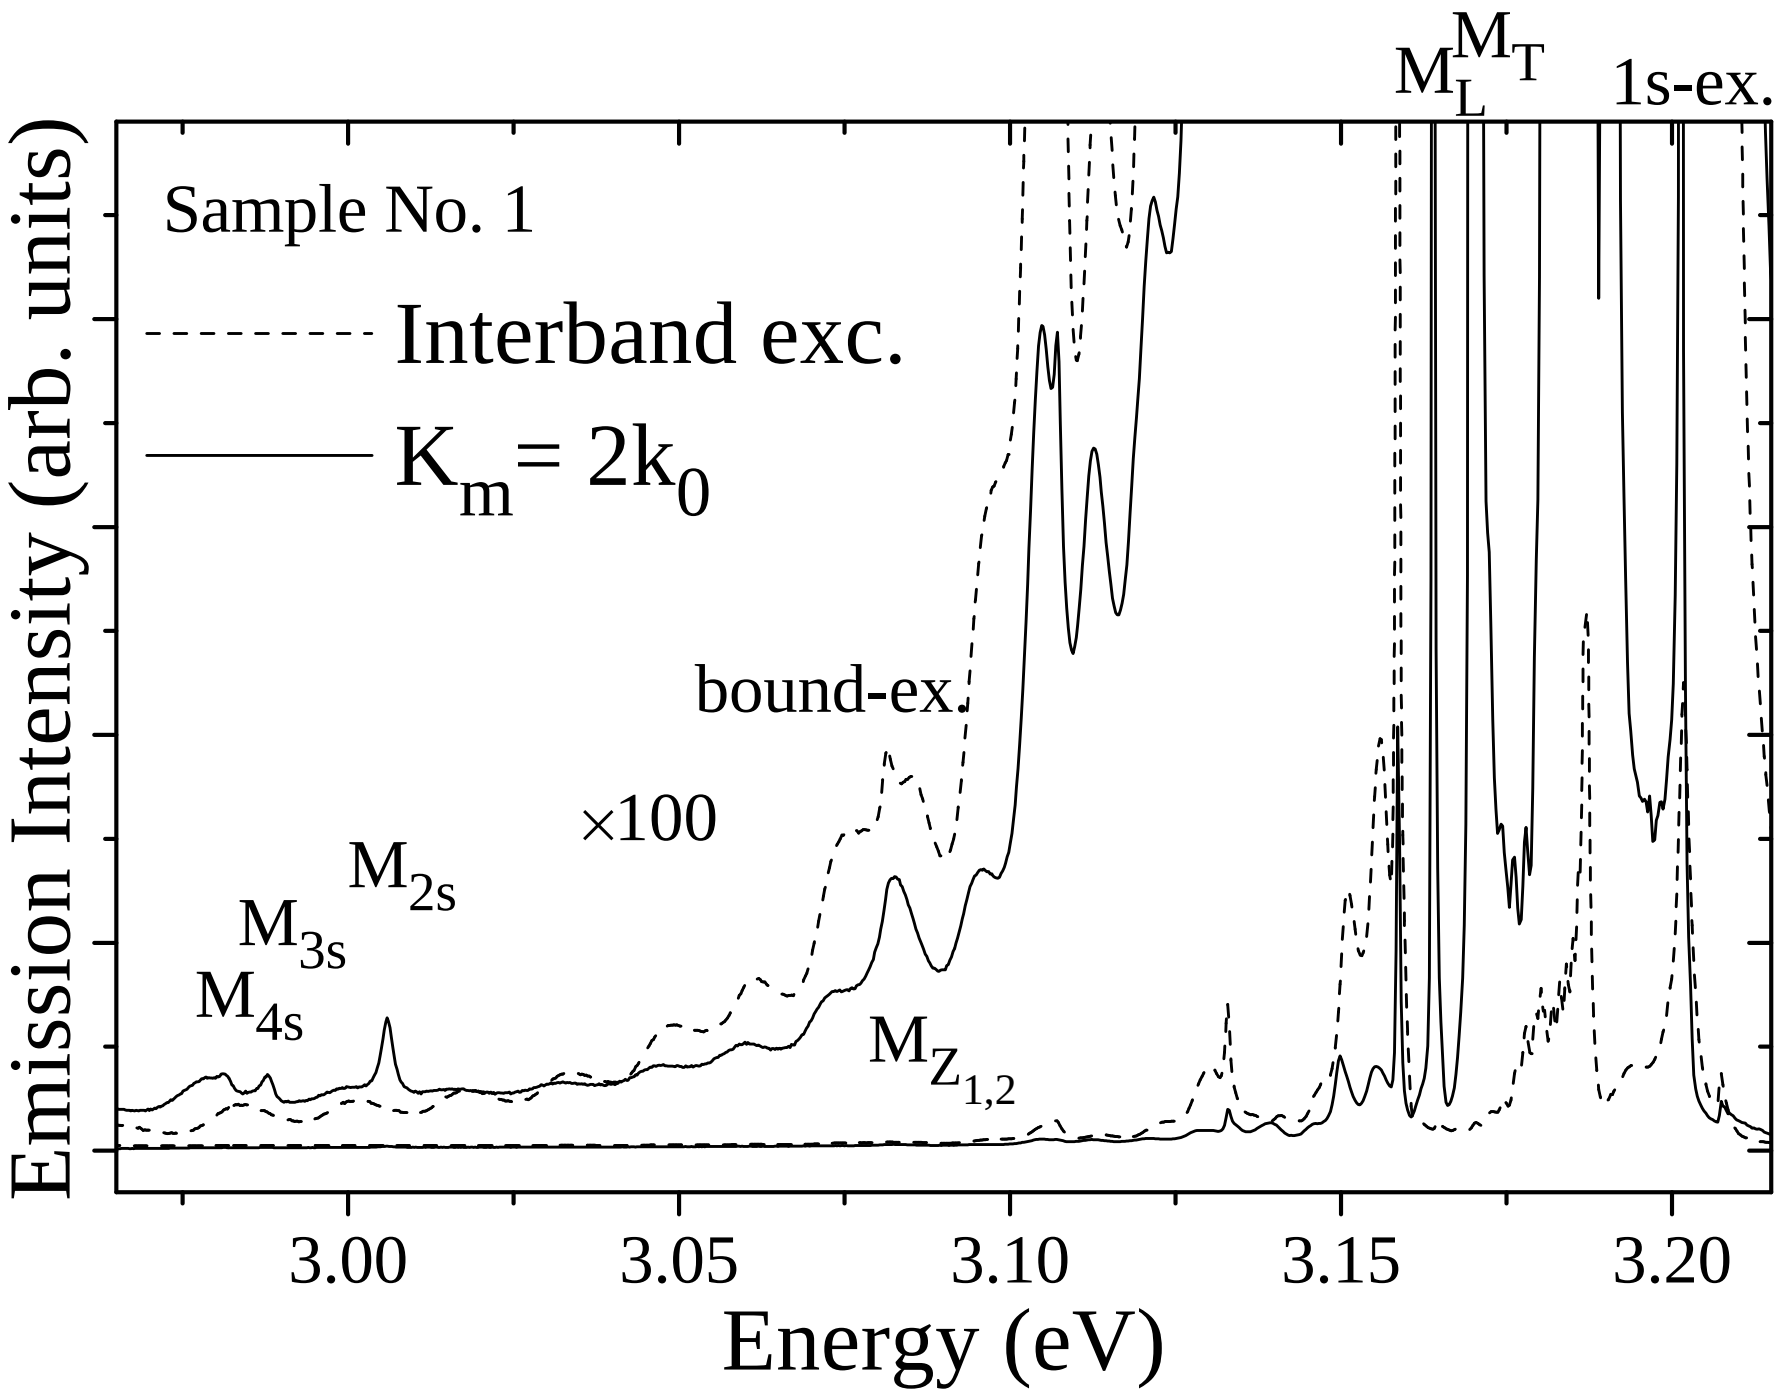
Sample No. 1
Interband exc.
$K_m = 2k_0$
Emission Intensity (arb. units)
Energy (eV)
3.00
3.05
3.10
3.15
3.20
M_{4s}
M_{3s}
M_{2s}
×100
bound-ex.
$M_{Z_{1,2}}$
M_L
M_T
1s-ex.

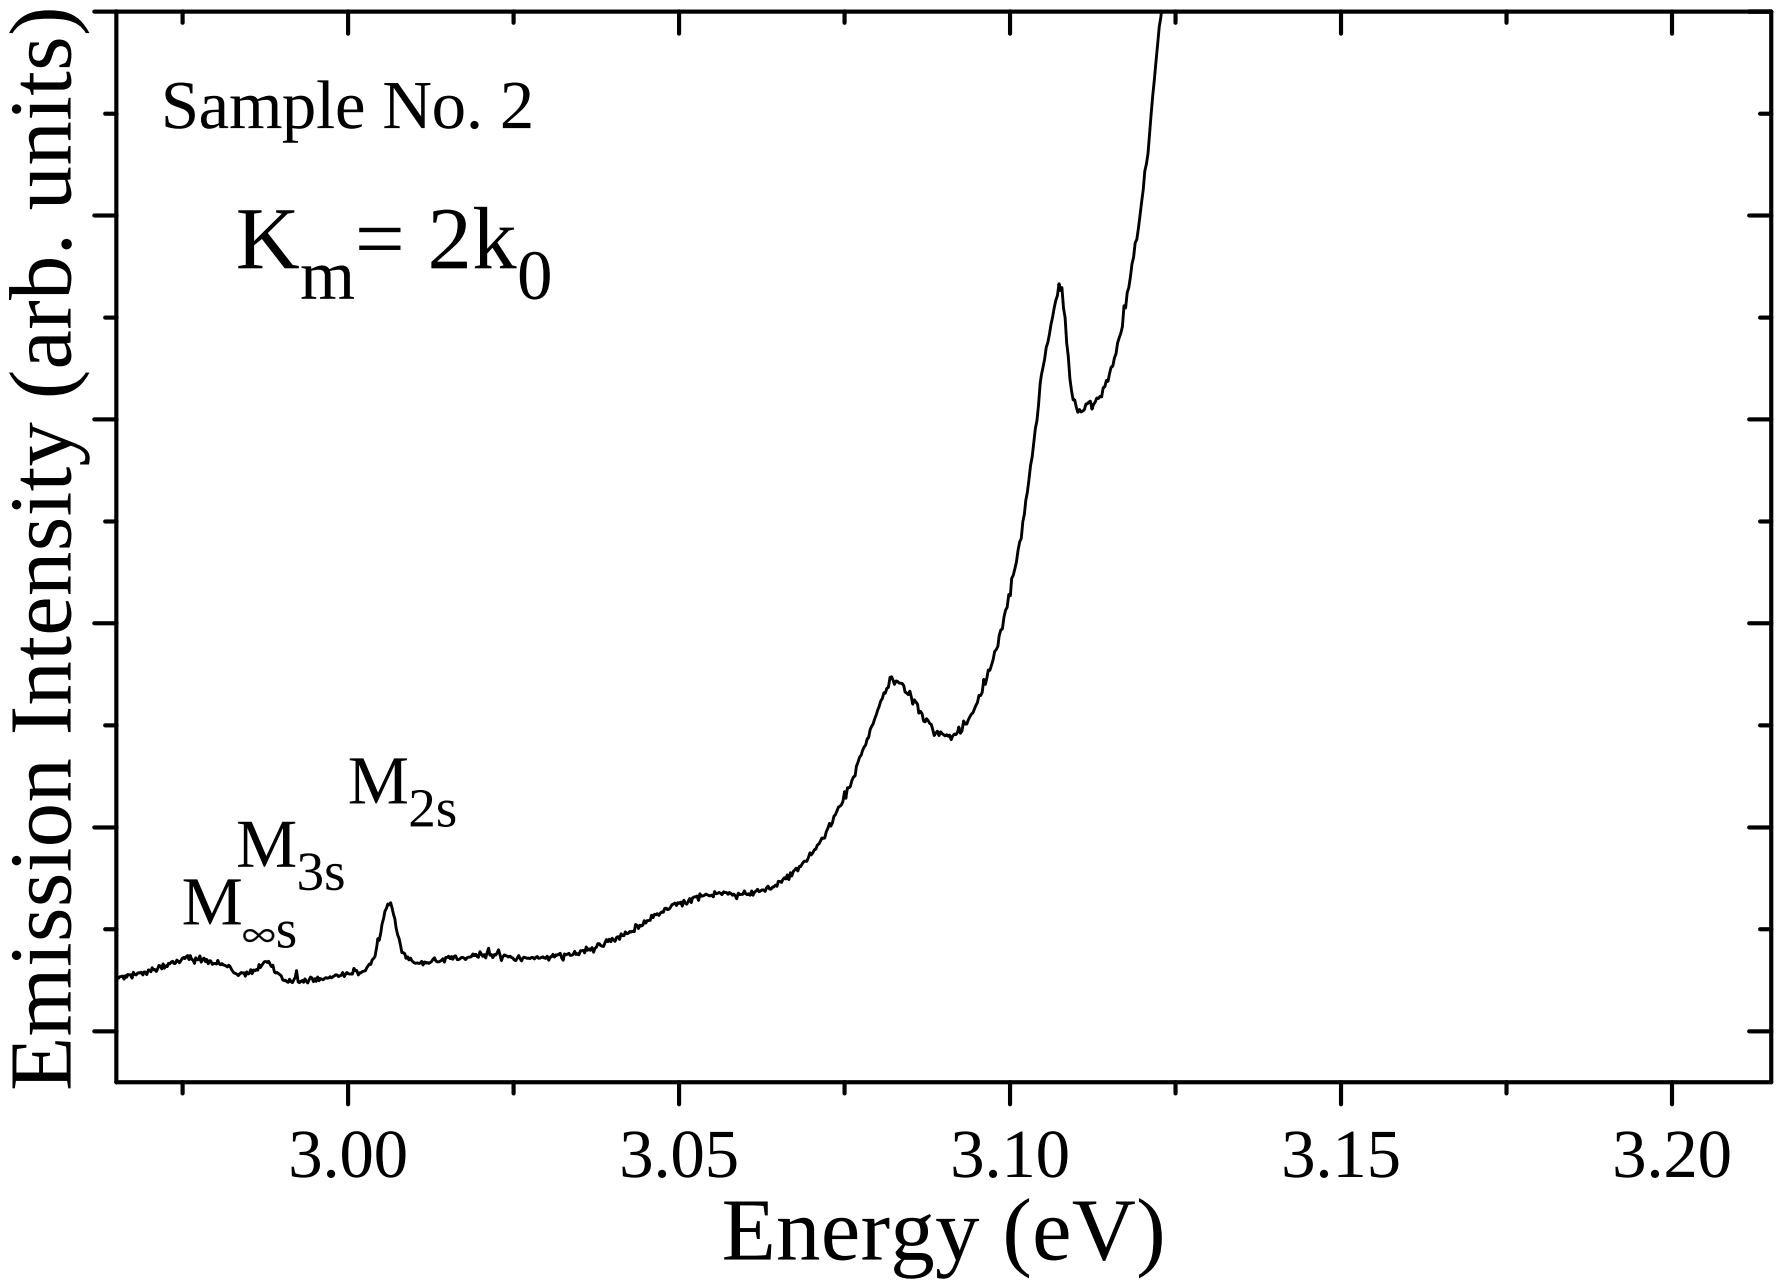
Sample No. 2
$K_m = 2k_0$
M_{2s}
M_{3s}
$M_{\infty s}$
Emission Intensity (arb. units)
3.00
3.05
3.10
3.15
3.20
Energy (eV)

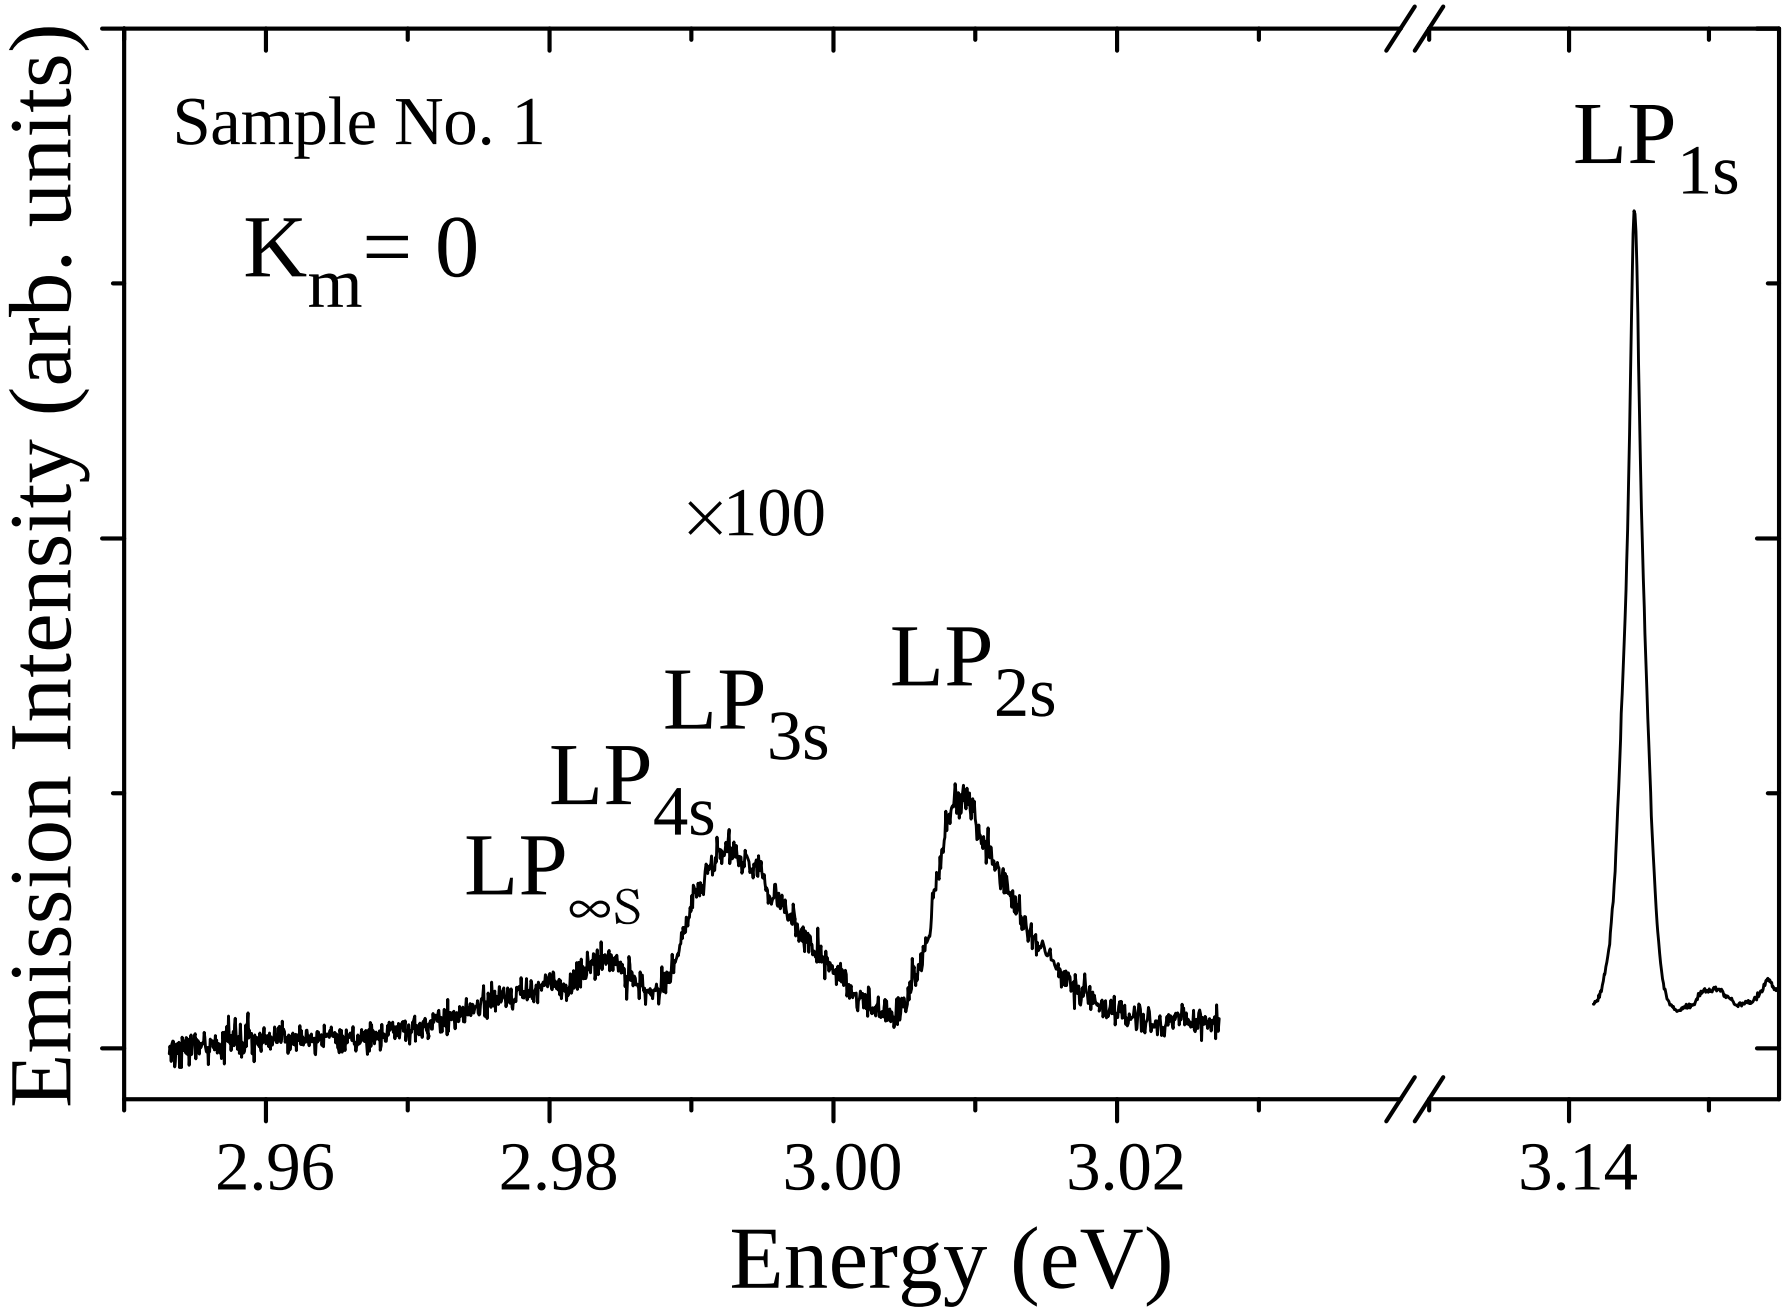
Sample No. 1
$K_m = 0$
LP_{1s}
×100
LP_{2s}
LP_{3s}
LP_{4s}
$LP_{\infty s}$
Emission Intensity (arb. units)
2.96
2.98
3.00
3.02
3.14
Energy (eV)